


Cation-mediated gelation of the fucose-rich polysaccharide FucoPol: preparation and characterization of hydrogel beads and their cytotoxicity assessment

Journal:	<i>The International Journal of Polymeric Materials and Polymeric Biomaterials</i>
Manuscript ID	Draft
Manuscript Type:	Full Research Paper
Date Submitted by the Author:	n/a
Complete List of Authors:	Araujo, Diana; Faculdade de Ciências e Tecnologia, Universidade NOVA de Lisboa, UCIBIO-REQUIMTE, Departamento de Química Fialho, Leticia; Faculdade de Ciências e Tecnologia, Universidade NOVA de Lisboa, UCIBIO-REQUIMTE, Departamento de Química Alves, Vítor; Universidade de Lisboa Instituto Superior de Agronomia, Linking Landscape, Environment, Agriculture and Food Roma-Rodrigues, Catarina; Faculdade de Ciências e Tecnologia, Universidade NOVA de Lisboa, UCIBIO-REQUIMTE, Departamento de Ciências da Vida Baptista, Pedro; Faculdade de Ciências e Tecnologia, Universidade NOVA de Lisboa, UCIBIO-REQUIMTE, Departamento de Ciências da Vida Fernandes, Alexandra; Faculdade de Ciências e Tecnologia, Universidade NOVA de Lisboa, UCIBIO-REQUIMTE, Departamento de Ciências da Vida Freitas, Filomena; FCT-UNL, UCIBIO-REQUIMTE, Chemistry Department Reis, Maria; Faculdade de Ciências e Tecnologia, Universidade NOVA de Lisboa, UCIBIO-REQUIMTE, Departamento de Química
Keywords:	FucoPol, hydrogel beads, cytotoxicity

SCHOLARONE™
Manuscripts

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41

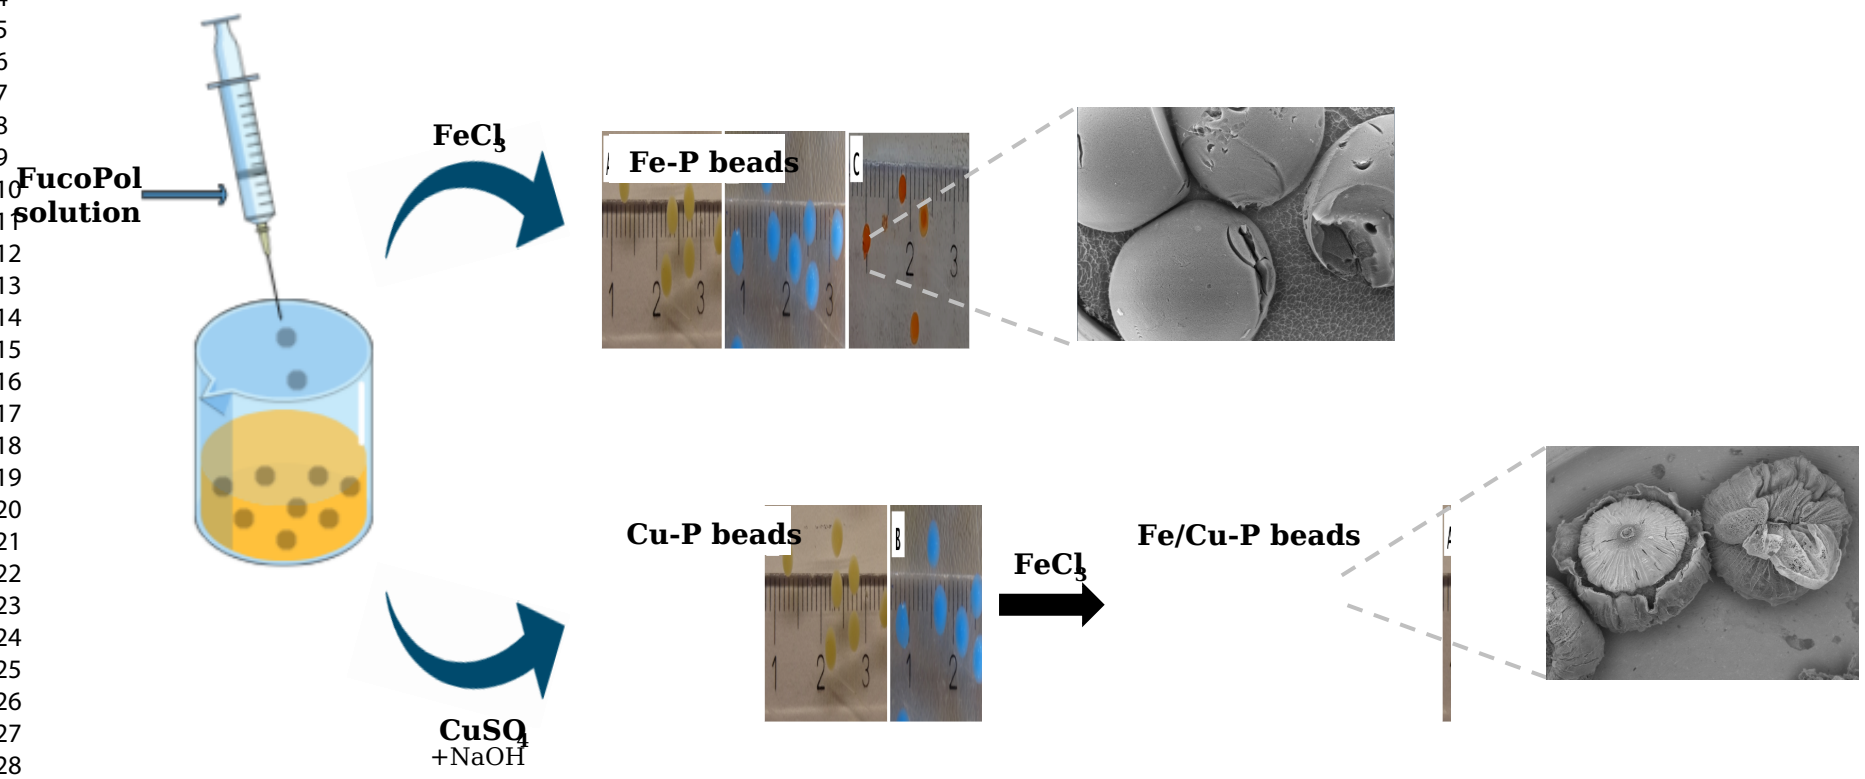

1
2
3 **Cation-mediated gelation of the fucose-rich polysaccharide FucoPol:**
4 **preparation and characterization of hydrogel beads and their cytotoxicity**
5 **assessment**
6
7

8
9 Leticia Fialho^{a,b}, Diana Araújo^a, Vitor D. Alves^c, Catarina Roma-Rodrigues^b,
10 Pedro V. Baptista^b, Alexandra R. Fernandes^{b,*}, Filomena Freitas^{a,*} and Maria A.
11 M. Reis^a
12
13
14

15
16 ^aUCIBIO-REQUIMTE, Chemistry Department, Faculdade de Ciências e Tecnologia,
17 Universidade Nova de Lisboa, Portugal
18

19
20 ^bUCIBIO, Departamento Ciências da Vida, Faculdade de Ciências e Tecnologia,
21 Universidade Nova de Lisboa, Portugal
22

23
24 ^cLEAF, Linking Landscape, Environment, Agriculture and Food, Instituto Superior de
25 Agronomia, Universidade de Lisboa, Portugal
26
27
28
29
30

31 * Corresponding authors
32

33
34 Filomena Freitas, UCIBIO-REQUIMTE, Chemistry Department, Faculty of Sciences and
35 Technology, Universidade NOVA de Lisboa, Campus da Caparica, 2829-516 Caparica,
36 Portugal; Tel.: +351 212948300; Email: a4406@fct.unl.pt
37
38

39
40 Alexandra R Fernandes, UCIBIO, Departamento Ciências da Vida, Faculdade de Ciências e
41 Tecnologia, Universidade NOVA de Lisboa, Campus da Caparica, 2829-516 Caparica,
42 Portugal; Tel.: +351 212948300; Email: ma.fernandes@fct.unl.pt
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Cation-mediated gelation of the fucose-rich polysaccharide FucoPol: preparation and characterization of hydrogel beads and their cytotoxicity assessment

This study describes for the first time the iron- and copper-mediated gelation of FucoPol, fucose-rich bacterial polysaccharide. The ability of FucoPol to gel in the presence of metal cations, including iron(III) and copper(II), was used for the preparation of hydrogel beads. Iron mediated the formation of stable and not cytotoxic gel beads, while copper resulted in fragile and cytotoxic ones. Copper-mediated beads coated with an iron-mediated gel layer were more stable and had reduced cytotoxicity. The resulting polymeric structures had differing morphology, physical properties and cytotoxicity, which support their use in several applications, including biomedicine, agriculture and bioremediation.

Keywords: FucoPol; hydrogel beads; cytotoxicity

1. Introduction

Hydrogels are three-dimensional, hydrophilic, polymeric networks, with chemical or physical cross-links, which can be cast into various shapes and retain high amounts of water or biological fluids^[1, 2]. The water retention properties of hydrogels are dependent on the polymers' composition and are mainly due to the presence of hydrophilic groups (e.g., carboxyl, hydroxyl). The swelling degree is also dependent on the cross-link density and nature^[2]. Hydrogels have highly porous structures, with soft and elastic mechanical characteristics, which make their properties similar to those of biological tissues^[2, 3].

Polysaccharides, due to their hydrophilic nature, together with their non-toxicity and biodegradability, are especially suitable for the preparation of hydrogels for different kinds of applications^[3-5]. Cation-mediated gelation of negatively charged polysaccharides is frequently used to obtain polysaccharide hydrogels, in which gelation occurs through the linkage of polymer chains mediated by ions^[5, 6]. The gelation mechanism involves the interaction of cations (e.g., calcium, copper, iron) with the polymers' negatively charged

1
2
3 residues, resulting in ionic crosslinks between different polymer chains^[5, 7]. Several natural
4 polysaccharides, including alginate^[3, 8], carrageenan^[9], gellan gum^[10, 11] and pectin^[12] were
5 used for the preparation of cation-mediated hydrogels.
6
7

8
9 Polysaccharide hydrogel beads can be obtained through ionotropic gelation by adding
10 dropwise the polymeric solution, through a needle, into an aqueous solution containing
11 polyvalent cations (e.g., Ca²⁺, Cu²⁺, Al³⁺)^[13, 14]. The particles thus obtained have the rigidity
12 of a soft solid conferred by the gel network and are permeable to small molecules and ions.
13 Given these properties, polysaccharide hydrogel beads find applications ranging from
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

22 FucoPol is a high molecular weight ($1.7 \times 10^6 - 5.8 \times 10^6$ Da) fucose-containing
23 polysaccharide secreted by the bacterium *Enterobacter* A47 (DSM 23139)^[19, 20]. FucoPol's
24 repeating unit is a hexamer with two fucose, two galactose, one glucose and one glucuronic
25 acid residues, corresponding to a molar ratio of 2.0:1.3:0.9:0.5^[20, 21]. The main chain is
26 composed of two α -(1,4)-linked fucose residues and a β -linked glucose residue, being one of
27 the fucose residues branched at position 3. The branches are composed of 2 galactose and a
28 glucuronic acid residue, with the terminal galactose residue pyruvated at positions 4 and 6. It
29 also contains acyl groups (succinyl, pyruvyl and acetyl) that account for up to 22wt% of the
30 polymer's weight^[20, 21]. The presence of glucuronic acid, as well as the acyl substituents
31 succinyl and pyruvyl, confer the polymer an anionic character^[21].
32
33
34
35
36
37
38
39
40
41
42
43

44 FucoPol forms viscous solutions with a shear thinning behaviour^[22], has film-forming
45 capacity and emulsion forming and stabilizing capacity^[20, 21]. In addition, it was used for
46 microencapsulation of bioactive compounds by spray drying^[23]. It was also employed as a
47 coating material for iron oxide magnetic nanoparticles and tested for human antibody
48 purification^[24] and for cell labelling by Magnetic Resonance Imaging^[25].
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 FucoPol's ability to form gels has never been assessed, but the polymer's polyanionic
4 character and high molecular weight has driven the interest on testing this valuable property.
5 Therefore, in this study, the gel-forming capacity of FucoPol was studied, particularly in the
6 presence of metal cations. Different salts were tested, including mono-, di- and trivalent metal
7 cations, and the ones that resulted in the formation of a gel were tested for the preparation of
8 beads. FucoPol gel beads were characterized in terms of physical-chemical properties,
9 morphology, stability in aqueous solution, metal release and cytotoxicity.
10
11
12
13
14
15
16
17
18

19 **2. Experimental**

20 ***2.1. Screening of cations for metal induced gelation of FucoPol***

21
22 Salts of several metal cations were tested, including monovalent (NaCl, KCl), divalent
23 (CaCl₂, MgSO₄, CuSO₄, ZnSO₄) and trivalent (FeCl₃) cations. A FucoPol solution (10 g L⁻¹)
24 was prepared by dissolving the polymer in deionized water and stirring for 1 hour, at room
25 temperature (25 °C). The gelation ability of the polymer was assessed according to the
26 procedure described by Shimada et al.^[26] with slight modifications. Briefly, 10 mg of each
27 salt was dissolved in 1 mL of either NaOH 2 M (alkaline conditions) or deionized water
28 (neutral conditions). Then, a volume of 4 mL of the FucoPol solution was mixed with the salt
29 solutions.
30
31
32
33
34
35
36
37
38
39
40
41
42
43

44 ***2.2. Preparation of FucoPol hydrogel beads***

45
46 A FucoPol solution (10 g L⁻¹) was prepared as described above and used for the preparation
47 of the metal-FucoPol hydrogel beads. For the preparation of iron(III)-FucoPol beads (Fe-P
48 beads), 1 mL of the FucoPol solution was dripped into 30 mL of an aqueous FeCl₃ solution
49 (1.3×10⁻⁵ mM) through a needle with a 0.6 mm diameter. The mixture was kept under stirring
50 (300 rpm), at room temperature (25 °C), for 30 minutes. Then, for removal of the unreacted
51
52
53
54
55
56
57
58
59
60

crosslinker, the beads were washed with deionized water (30 mL; 4 times) until the pH was 6.5-7.5, and the conductivity was below $10 \mu\text{S cm}^{-1}$.

For preparation of the copper(II)-FucoPol beads (Cu-P beads), 50 mg of CuSO_4 dissolved in 1 mL deionized water were mixed with 2 mL of the FucoPol solution. The resulting solution was dripped into 30 mL of a NaOH 2 M through a needle with a 0.6 mm diameter. The mixture was kept under stirring (300 rpm) at room temperature (25 °C). The Cu-P beads were removed from the solution 2 min after being formed and placed in deionized water for removal of unreacted NaOH and CuSO_4 . The beads were washed 4 times with deionized water (30 mL) until reaching neutral pH and a conductivity value below $10 \mu\text{S cm}^{-1}$. Iron(III)/Cu(II)-FucoPol beads (Fe/Cu-P beads) were obtained by transferring Cu-P beads, prepared as described above, into an aqueous FeCl_3 solution (1.3×10^{-5} mM). The beads were kept under stirring for 15 min (at 300 rpm).

2.3. Characterization of the beads

The metal-FucoPol beads were characterized in terms of their morphology (shape and size) by scanning electron microscopy (SEM), and colour. SEM was performed with a Tabletop Microscope TM3030 (Hitachi in high technologies, America). Hydrated samples were observed at low temperature (-4 °C) with a magnification in the range of 30 - 1200×. The dried beads, obtained by freeze-drying the hydrogel beads, were analyzed by fourier transform infrared spectroscopy (FTIR) and thermogravimetric analysis (TGA). FTIR analysis was conducted with a Perkin-Elmer Spectrum two spectrometer. The spectra were recorded between 400 and 4000 cm^{-1} resolution with 10 scans, at room temperature. TGA was performed using a thermogravimetric equipment Labsys EVO (Setaram, France). The samples were placed in aluminium crucibles and analysed in the temperature range between 25 and 500 °C, at $10 \text{ °C} \cdot \text{min}^{-1}$. For quantification of the beads' metal content, they were

1
2
3 placed in deionized water and hydrolyzed with 10% (v/v) trifluoroacetic acid (TFA), at 120 °C,
4
5 for 4 hours. The samples were filtered (0.45 µm nylon; WHATMAN) and their content in
6
7 iron and copper was determined by Inductively coupled plasma – atomic emission
8
9 spectroscopy (ICP-AES) (Horiba Jobin-Yvon, France, Ultima model) equipped with a 40.68
10
11 MHz RF generator, Czerny-Turner monochromator with 1.00 m (sequential), autosampler
12
13 AS500 and Concomitant Metals Analyzer (CMA).
14
15

16 17 **2.4. Metal release from the FucoPol beads**

18
19 The metal release from the FucoPol beads was evaluated in different aqueous media:
20
21 deionized water, physiological serum (NaCl 0.9%, w/v), simulated gastric fluid (SGF)
22
23 without pepsin (NaCl 30 mM, HCl 0.3% (v/v), pH 1.2 ± 0.1), simulated intestinal fluid (SIF)
24
25 without pancreatin (KH₂PO₄ 50 mM, NaOH 0.015 N, pH 6.8 ± 0.1), phosphate-buffered
26
27 saline (PBS, KH₂PO₄ 1 mM, Na₂HPO₄ 3 mM, NaCl 155 mM, KCl 30 mM, pH 7.4) and cell
28
29 culture medium Dulbecco's Modified Eagle Medium (DMEM, ThermoFisher Scientific,
30
31 Waltham, Massachusetts, USA) supplemented with 10 % (v/v) heat inactivated fetal bovine
32
33 serum (FBS, ThermoFisher Scientific) and a mixture of 100 U/mL penicillin and 100 µg/mL
34
35 streptomycin (ThermoFisher Scientific). To evaluate the metal release over time in each
36
37 solution, FucoPol beads were weighed (150 mg Cu-P, 100 mg Fe-P or 30 mg Fe/Cu-P beads),
38
39 placed in 30 mL of each medium and kept at room temperature (25 °C) for 48 hours, in an
40
41 orbital shaker, at 150 rpm. Metal quantification was performed by ICP-AES, as described
42
43 above. This test was also performed at 37 °C for DMEM-FBS. Results were normalized to
44
45 time 0 hours.
46
47
48
49
50

51 **2.5. Biological assays**

52 **2.5.1. Cell culture**

53
54
55
56
57
58
59
60

1
2
3 Normal human primary dermal fibroblasts, HPDFs; ovarian carcinoma cell line,
4 A2780; breast adenocarcinoma cell line, MCF-7; lung adenocarcinoma cell line, A549;
5 and chronic myeloid leukemia cell line, K562 (ATCC, Manassas, Virginia, USA) were
6 used. A549 cell line was cultured in DMEM-FBS; MCF-7, HPDFs and K562 were
7 cultured in DMEM-FBS supplemented with 1% (v/v) MEM (Minimum Essential
8 Media) non-essential amino acids (ThermoFisher Scientific) and A2780 cell line was
9 cultured on RPMI-1640 medium (ThermoFisher Scientific) supplemented with 10%
10 FBS and a mixture of 100 U/mL penicillin and 100 mg/mL streptomycin^[27, 28]. All cell
11 cultures were maintained at 37 °C, 5 % (v/v) CO₂, 99 % (v/v) relative humidity.
12
13
14
15
16
17
18
19
20
21
22

23 2.5.2. Cytotoxicity via MTS assay

24 Cytotoxicity analysis of FucoPol in normal and tumor cells (HPDFs, A2780, A549,
25 K562 and MCF-7) was performed as previously described by Fernandes et al.^[29].
26 Briefly, cells were seeded in 96 well plates at a density of 0.75×10^4 cells per well. The
27 culture medium was removed 24 h after seeding and replaced with fresh DMEM-FBS
28 containing FucoPol at concentrations between 0-500 $\mu\text{g mL}^{-1}$. Two controls were used
29 in each experiment, one without supplementation of FucoPol and another for assessing
30 FucoPol interference in the MTS assay using an identical 96 well plate without cells.
31 Cell viability was assessed after 48 h incubation using the CellTiter 96[®] AQueous One
32 Solution Cell Proliferation Assay Kit (Promega, Madison, EUA), according to the
33 manufacturer's instructions. After cell incubation with FucoPol, the supernatant was
34 removed and replaced by fresh medium supplemented with 20 % (v/v) MTS solution.
35 After an incubation period of 45 min at 37 °C, 5% (v/v) CO₂ and 99% (v/v) relative
36 humidity, the absorbance at 490 nm was determined using a Tecan Infinite F200
37 Microplate Reader (Tecan, Männedorf, Switzerland). The obtained data was
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 normalized relative to control samples to obtain cell viability (%) for each FucoPol
4
5 concentration using the following equation:

$$6 \quad \text{cell viability (\%)} = \frac{\text{Abs}_{490} \text{ with cells} - \text{Abs}_{490} \text{ without cells}}{\text{Abs}_{490} \text{ control with cells} - \text{Abs}_{490} \text{ control without cells}} \times 100 \quad (1)$$

11 2.5.3. Cytotoxicity via trypan blue

12
13
14 The cytotoxicity of FucoPol and FucoPol beads was also evaluated on K562 cell line
15
16 using the Trypan Blue Exclusion method according to Strober^[30]. Cells were seeded
17
18 on a 24-well plate at a density of 2.5×10^4 cells per well in DMEM-FBS supplemented
19
20 with increasing concentrations of FucoPol ($0-500 \mu\text{g mL}^{-1}$) or FucoPol beads (3-4
21
22 beads were used in each well, corresponding to a mass of 40, 150 or 17 mg for the Fe-
23
24 P, Cu-P or Fe/Cu-P beads, respectively). Control assays were also conducted. After 48
25
26 h incubation, the cellular suspension was mixed with 0.4 % (w/v) Trypan Blue
27
28 (ThermoFisher Scientific) in a 4:1 proportion (cells: trypan blue). The mixture was
29
30 loaded on a hemocytometer (Hirschmann, Eberstadt, Germany) and the number of
31
32 viable cells was counted in an Olympus CXX41 inverted microscope (Tokyo, Japan).
33
34
35

37 3. Results and Discussion

40 3.1. Screening of cations for metal induced gelation of FucoPol

41
42 As shown in Table 1 and Figure 1, under neutral pH conditions, no gelation of FucoPol was
43
44 observed, except in the presence of the trivalent cation Fe^{3+} . Under the conditions tested,
45
46 upon mixing the polymer solution with the FeCl_3 solution, a strong gel was formed. For all
47
48 other salts tested, no significant changes in the mixtures were observed (Figure 1, upper
49
50 image). However, under alkaline conditions, gel formation was observed in the presence of
51
52 the divalent cation Cu^{2+} (Figure 1, lower image). No changes were observed in the presence
53
54
55
56
57
58
59
60

of the tested monovalent cations (Na^+ and K^+) or the divalent cation Zn^{2+} , while Ca^{2+} lead to the formation of a white precipitate (Table 1).

Since among the tested salts, FeCl_3 and CuSO_4 resulted in the formation of the strongest gels, these salts were selected to prepare FucoPol gel beads.

3.2. *FucoPol gel beads*

Given the ability of FucoPol to gel under neutral pH conditions, Fe-P beads were prepared by dripping the polymer solution into a FeCl_3 solution. Yellow spherical gel beads with 2.0-3.0 mm diameter were spontaneously formed (Figure 2-A). The beads had an average mass of 7.90 ± 0.002 mg, with a water content of $98.60 \pm 0.26\text{wt}\%$ (Table 2). Their iron content was 11.54 ± 1.09 μg per bead, thus corresponding to $0.15 \pm 0.01\text{wt}\%$ of the beads' mass. Therefore, the beads' metal-to-polymer ratio was only $0.12 \text{ mg}_{\text{Fe}}/\text{mg}_{\text{FucoPol}}$. The formed structures were stable, withstanding over 6 months in deionized water at room temperature (25°C), without any visible alteration of their shape, size or color.

The Cu-P beads were prepared under alkaline conditions by dripping the polymer solution containing CuSO_4 into a NaOH 2 M solution. The beads were also spherical but had a blue color and were larger than the Fe-P beads, displaying a mean diameter of 3.0-4.0 mm (Table 2, Figure 2-B). Concomitantly, the beads had a considerably higher mass (50.59 ± 0.006 mg) than the Fe-P beads and a higher water content ($99.84 \pm 0.06\text{wt}\%$) (Table 2). The beads had a copper content of 134.50 ± 29.63 μg per bead, which corresponded to $0.27 \pm 0.06\text{wt}\%$ of their mass. Comparing to the Fe-P, the Cu-P beads were rather fragile, swallowing and disintegrating after 24 hours in deionized water at room temperature (25°C). This lower stability may be related to the fact that the metal-to-polymer ratio was considerable higher ($1.66 \text{ mg}_{\text{Cu}}/\text{mg}_{\text{FucoPol}}$) than that of the Fe-P beads ($0.12 \text{ mg}_{\text{Fe}}/\text{mg}_{\text{FucoPol}}$). The low polymer content of the beads has resulted probably in a weaker gel network.

1
2
3 In an attempt to obtain more stable copper containing beads, Cu-P beads were
4 prepared and placed in a FeCl_3 solution. This strategy was successful since the resulting
5 Fe/Cu-P beads were stable for over 15 days in deionized water, at room temperature. These
6 beads had a dark orange color and were smaller than both the Fe-P and the Cu-P beads, with
7 a mean diameter of 1.5-2.0 mm (Table 2, Figure 2-C). They had a water content of
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

99.27±0.47wt%, similar to the Cu-P beads. The Fe/Cu-P beads had iron and copper contents of 11.84±3.21 and 118.33±20.54 $\mu\text{g}/\text{bead}$, respectively (Table 2), corresponding to metal-to-polymer ratios of 0.17 $\text{mg}_{\text{Fe}}/\text{mg}_{\text{FucoPol}}$ and 1.75 $\text{mg}_{\text{Cu}}/\text{mg}_{\text{FucoPol}}$, respectively. These results suggest that the Fe/Cu-P beads had a core made of Cu-mediated FucoPol gel, surrounded by an outer shell of Fe-mediated FucoPol gel that eventually stabilized the final Fe/Cu-P beads' structure.

3.3. *FucoPol gel beads characterization*

3.3.1. *Morphology*

The surface morphology of the prepared Fe-P and Fe/Cu-P hydrogel beads was observed by SEM (Figure 3 and 4). Given the fragility of the Cu-P beads, they disintegrated upon freezing, rendering their visualization by this technique not possible.

The Fe-P beads had a smooth surface but presented some fractures (Figure 3-A). Upon magnification of a bead's smooth surface, a rather homogeneous porous structure was observed (Figure 3-B). Moreover, different porous structures could be seen upon magnification of the fractured portions of the beads' surface (Figure 3-C and D).

The Fe/Cu-P beads presented a much more complex structure, with an almost spherical internal core surrounded by an outer shell (Figure 4-A and B). The core was attributed to an internal bead formed by gelation in the presence of copper, while the outer shell is envisaged to be formed when the Cu-P beads were placed in the FeCl_3 solution. Upon

1
2
3 magnification, different structures could be observed. The inner core seemed to be more
4 compact, presenting stretch marks emerging outwards from the center of the bead (Figure 4-
5 A.1). Upon a closer look (Figure 4-B.1), the structure of the inner core was actually rough
6 with pores of different shapes and sizes. The outer shell also presented striated and porous
7 structures (Figure 4-B.1) but was much less compact, as shown by their lacelike structure
8 (Figure 4-A.2 and B.2).
9
10
11
12
13
14

15 16 17 3.3.2. Fourier-transform infrared spectra analysis 18

19 FTIR analysis was carried out to understand the interaction between FucoPol's
20 functional groups and the metal cations. As shown in Figure 5, the FTIR spectrum of
21 Fe-P beads (full red line) mainly shows the bands characteristic of FucoPol (full grey
22 line)^[21] which is in accordance with the low metal-to-polymer ratio of the Fe-P gel
23 beads (0.10 mg_{Fe}/mg_{FucoPol}). Nevertheless, it can be seen that the interaction of FucoPol
24 with iron led to shifts of several absorption peaks, especially those attributed to the
25 hydroxyl and carboxylate groups. The broad and intense band corresponding to the
26 stretching frequencies of hydroxyl groups (O–H), observed at 3300 cm⁻¹ for FucoPol
27 (Figure 5-full grey line), was shifted to 3275 cm⁻¹ in the Fe-P spectrum (Figure 5-full
28 red line). The absorption peaks at 1722 and 1016 cm⁻¹ that can be attributed to the C=O
29 stretching of the carbonyl moieties found in the acyl substituents^[21] and to C–O and C–
30 C vibrations of the glycosidic bonds and pyranoid ring^[31], respectively, were shifted to
31 1720 and 1023 cm⁻¹. The C-H stretching peak of CH₂ groups^[32] appearing at 2925 cm⁻¹
32 was also shifted to a lower wavenumber (2922 cm⁻¹). The peak at 1600 cm⁻¹ and the
33 absorption region at 1370-1400 cm⁻¹ that can be attributed to the asymmetric and
34 symmetric stretching of carboxylates from glucuronic acid^[31] were also shifted to 1635
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 cm^{-1} and $1380\text{-}1418\text{ cm}^{-1}$, respectively. Similarly, the band at 1254 cm^{-1} that may also
4
5 be attributed to the C-O-C vibration of acyls^[33] was shifted to 1260 cm^{-1} .
6

7
8 Regarding the Cu-P and Fe/Cu-P beads, although the FTIR spectra shows the same
9
10 main peaks (Figure 5-dotted and dashed lines, respectively) displayed by FucoPol, they are
11
12 much less intense. This may be related to the high metal-to-polymer ratio of those beads. The
13
14 main difference is that the peak appearing at 1722 cm^{-1} in FucoPol spectrum was is no longer
15
16 observed in neither the Cu-P or the Fe/Cu-P beads spectra, suggesting that the carbonyl
17
18 moieties found in the acyl substituents were involved in the interaction between the polymer
19
20 chain and the metals. Moreover, two new peaks are observed at 3580 and 680 cm^{-1} in both
21
22 copper-containing beads spectra, which may be indicative of the presence of $\text{Cu}(\text{OH})_2$ formed
23
24 upon exposure of Cu(II) to NaOH during the preparation of the beads. The peak at 3580 cm^{-1}
25
26 may reflect stretching modes of the hydroxyl groups in $\text{Cu}(\text{OH})_2$, while the peak at 680 cm^{-1}
27
28 might correspond to the C-O stretching vibration of Cu^{2+} in $\text{Cu}(\text{OH})_2$ ^[34].
29
30

31 32 3.3.3. Thermogravimetric analysis

33
34
35 The thermal degradation curves of FucoPol and Fe-P beads (Figure 6) presented three
36
37 mass loss regions. For FucoPol (full grey line) and the Fe-P beads (full red line), the
38
39 first mass loss, of around 15%, was observed within $35\text{-}140\text{ }^\circ\text{C}$ and $35\text{-}150\text{ }^\circ\text{C}$,
40
41 respectively, and can be attributed to water evaporation^[23]. The higher temperature
42
43 range observed for the Fe-P beads sample suggests that water is bound more strongly in
44
45 the beads than in FucoPol. The largest mass loss (around 50%) occurred between 180
46
47 and $380\text{ }^\circ\text{C}$ and is probably associated with the polysaccharide's side chains
48
49 decomposition^[35]. The third mass loss comprised a gradual weight loss observed above
50
51 $380\text{ }^\circ\text{C}$ that is probably associated with the polysaccharide' main-chain scission
52
53 degradation^[35]. Char yields of 24% and 25% were obtained for FucoPol and the Fe-P
54
55
56
57
58
59
60

1
2
3 beads, respectively. These results show that the thermal properties of FucoPol were not
4
5 significantly altered by the presence of iron in the Fe-P beads.
6

7 For the Cu-P and Fe/Cu-P beads (Figure 6, dotted and dashed lines, respectively),
8
9 there was a gradual mass loss of around 11% between 35 and 170 °C, associated with water
10
11 evaporation. The lower mass loss observed for these beads might be related with the
12
13 considerably lower polymer content in the copper-containing beads. The largest mass losses
14
15 occurred within 170-430 °C in which around 38% of the samples' mass was degraded,
16
17 resulting in a final char yield of 51-53%. The higher char yield is probably related with the
18
19 significantly higher metal content of the Cu-P and Fe/Cu-P beads.
20
21
22

23 **3.4. Metal release from the FucoPol beads**

24
25
26 The metal release from the FucoPol gel beads was evaluated in different aqueous solutions
27
28 (Table 3) representing some biological contexts of *in vitro* studies (PBS and DMEM-FBS) or
29
30 simulating human body environments after oral ingestion of the beads (SGF, SIF and
31
32 physiological serum).
33

34
35 All beads disintegrated in SGF in only a few minutes after exposure to the medium
36
37 (Table 3). However, the polymer was not degraded, suggesting the low pH of the medium
38
39 (pH 1.2 ± 0.1) may have destabilized the gel structure, leading to bead disaggregation and,
40
41 consequently, polymer dissolution. In all the other tested media, the beads kept their integrity,
42
43 although in some cases they swelled, and their shape or size were altered.
44

45
46 Regarding the Fe-P beads, there was no significant iron release in water, physiological
47
48 serum or DMEM-FBS (Table 3), and the beads remained unchanged during the 24 h of the
49
50 assay. However, in PBS solution and SIF, the iron release was 0.18 ± 0.02 and 0.19 ± 0.02
51
52 mg/L, respectively, that correspond to only 3.7 and 3.9% of the beads' iron content. The iron
53
54 release observed in PBS and SIF may be related to the solutions' pH that was around 6.8-7.4,
55
56
57
58
59

1
2
3 while for deionized water and physiological serum it was 5.5-5.8. Moreover, the higher salts
4 concentration of PBS and SIF compared to deionized water and the physiological serum may
5 also have impacted on the release of iron from the beads. The presence of additional cations
6
7 (K^+ , Na^+) and anions (PO_4^{3-} , Cl^-) may have interfered on the interaction between the polymer
8 chain and Fe^{3+} .
9
10

11
12
13 Considering the Cu-P beads, although their shape was maintained during the assays in
14 water, physiological serum and PBS, they got progressively swelled over time. The beads
15 released on average $0.25 \pm 0.06 \text{ mg L}^{-1}$ of copper in deionized water, while $0.08 \pm 0.02 \text{ mg L}^{-1}$
16 were released in physiological serum and PBS (Table 3). These values represent less than 2%
17 of the beads' copper content. In SGF, DMEM-FBS and SIF, on the other hand, there was a
18 gradual decrease of the beads' size, being totally disintegrated within a few minutes, 6 min
19 and 24 min, respectively, thus releasing all their copper content into the media.
20
21
22
23
24
25
26
27
28

29 As for Fe/Cu-P beads, their shape was maintained during the assays in physiological
30 serum, DMEM-FBS, PBS and SIF, and only disintegrated in SGF (Table 3). These results
31 show that the iron-mediated gel layer formed over the copper-containing gel bead conferred
32 stability to the beads, allowing them to withstand the presence of SIF and DMEM-FBS
33 without the disintegration observed in those media for the single Cu-P beads. Moreover, there
34 was no significant iron release from the beads in any of the tested media, while copper
35 release was below 2% for most media (Table 3). The exception was DMEM-FBS, at 37°C, in
36 which a copper concentration of $0.98 \pm 0.17 \text{ mg L}^{-1}$ was detected, which corresponds to almost
37 8% of the beads' copper content. Since no copper release was noticed in DMEM-FBS at 25
38 °C, probably the higher temperature (37 °C) partially destabilized the gel structure and led to
39 copper release in this medium. Indeed, in this assay, the beads appeared to be more
40 translucent, thus indicating changes on their structure.
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55

56 **3.5. Biological evaluation**

57
58
59
60

3.5.1. Cytotoxic evaluation of FucoPol

The antiproliferative effect of FucoPol in a colorectal carcinoma cell line, HCT116, was previously described by Palma et al.^[25]. A reduction of 30% in HCT116 cell viability was observed after exposure of cells to FucoPol at a concentration of 138 $\mu\text{g/mL}$ for 48 h^[25]. In this study, FucoPol effect was evaluated in other tumor epithelial cell lines (including ovarian carcinoma cell line, A2780, lung adenocarcinoma cell line, A549, breast adenocarcinoma cell line, MCF-7, and in a chronic myelogenous leukaemia cell line, K562) and in normal human primary dermal fibroblasts, HPDFs.

Cell viability after 48 h of treatment with increasing concentrations of FucoPol was measured using the MTS assay, where the production of formazan is proportional to cell viability. No loss of HPDFs, A549, MCF-7, and K562 cell viability for concentrations of FucoPol up to 500 $\mu\text{g/mL}$ (Figure 7). In contrast, the A2780 tumor cell line showed to be more sensitive, compared to the other cell lines, with a reduction of cell viability of 30.5% for a FucoPol concentration of 500 $\mu\text{g/mL}$ (Figure 7-E). Considering these results and also those reported previously, FucoPol can be considered a safe polymer for further biological studies.

3.5.2. Cytotoxic evaluation of FucoPol beads

Considering that no loss of viability was observed with FucoPol in K562, this cell line was chosen for testing the Fe-P, Cu-P and Fe/Cu-P hydrogel beads using the Trypan-blue exclusion method^[30]. For comparison, the viability of free FucoPol was also evaluated in K562 cell line using the same. In accordance with results obtained in Figure 7-D, no alterations of viability were observed when K562 cells were exposed to 500 $\mu\text{g/mL}$ FucoPol (Figure 8).

1
2
3 As evidenced in Figure 9, the Fe-P beads are not cytotoxic for K562 cells during the
4 48 h of incubation period since a cell viability of $94.7 \pm 8.3\%$ was obtained. These results
5 agree with the fact that no iron release was observed from the beads upon exposure to
6 DMEM-FBS medium at $37\text{ }^\circ\text{C}$ (as shown in Table 3). Incubation of K562 cells with the Cu-P
7 beads resulted in a 55% cell viability decrease (Figure 9), that might be correlated with the
8 beads' disintegration with the concomitant release of their copper content. Since no cell
9 viability loss was observed in the presence of FucoPol (Figure 8), the reduced K562 cell
10 viability observed (Figure 9) can be attributed to the release of copper to the medium from
11 the Cu-P beads.
12
13
14
15
16
17
18
19
20
21

22 In fact, each bead had a copper content of $134.50 \pm 29.63\text{ }\mu\text{g}$, thus corresponding
23 to a concentration of around $201.75 \pm 177.78\text{ }\mu\text{g/mL}$ in each well. According to Ruiz et
24 al.^[36], exposure to copper concentrations above 100 mM (i.e., $6.35\text{ }\mu\text{g mL}^{-1}$) does not
25 induce K562 cells death but affects cell differentiation and proliferation. In this study,
26 K562 cells were exposed to a considerably higher copper concentrations that led to the
27 observed reduction of the cells' viability (Figure 9).
28
29
30
31
32
33
34

35 Concerning the Fe/Cu-P beads, there was a slight decrease in K562 cells viability of
36 21.4% that might be also correlated with the release of copper from the respective beads.
37 Although the beads did not disintegrate, they released copper upon cultivation in DMEM-
38 FBS medium (Table 3), resulting in a copper concentration of approximately 72.7 ± 12.6
39 $\mu\text{g/mL}$ in each well, which is already cytotoxic^[36].
40
41
42
43
44
45

46 The results presented here show the antiproliferative potential of Cu-P and Fe/Cu-P
47 beads per se (particularly the first ones) in K562 cells, thus supporting the future
48 incorporation of Imatinib in those beads towards increasing this antiproliferative effect and
49 their potential for chronic myeloid leukemia (CML) therapy^[37]. The Fe-P beads, on the other
50
51
52
53
54
55
56
57
58
59
60

1
2
3 hand, posed no cytotoxicity under the conditions tested, which supports their potential use as
4
5 drug delivery carriers.
6
7

8 **4. Conclusions**

10 This study demonstrates for the first time the potential of the fucose-rich polysaccharide
11
12 FucoPol for the development of polymeric structures by its cation-mediated gelation. Iron(III)
13
14 and/or copper(II) were used to obtain FucoPol hydrogels with different valuable properties
15
16 that envisage their use in distinct areas. The iron-containing gel beads, given their stability
17
18 and non-cytotoxicity, may be used, for example, for the development of drug delivery
19
20 carriers, while the copper-containing gel beads may find applicability in CML therapy due to
21
22 their antiproliferative action.
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Acknowledgements

This work was supported by the Unidade de Ciências Biomoleculares Aplicadas (UCIBIO) and LEAF-Linking Landscape, Environment, Agriculture and Food, which are financed by national funds from FCT/MEC (UID/Multi/04378/2019 and PEst-OE/AGR/UI0245/2014, respectively) and co-financed by the ERDF, under the PT2020 Partnership Agreement (POCI-01-0145-FEDER-007728 and POCI-01-0145-FEDER – 007265, respectively). FCT/MCTES is also acknowledged for scholarships SFRH/BD/140829/2018 and SFRH/BPD/124612/2016.

For Peer Review Only

References

- [1] Coviello, T.; Matricardi, P.; Marianecchi, C.; Alhaique, F. Polysaccharide hydrogels for modified release formulations. *J. Control. Release* **2007**, *119*, 5–24.
- [2] Biondi, M.; Borzacchiello, A.; Mayol, L.; Ambrosio, L. Nanoparticle-integrated hydrogels as multifunctional composite materials for biomedical applications. *Gels* **2015**, *1*, 162.
- [3] Marković, D.; Zarubica, A.; Stojković, N.; Vasić, M.; Cakić, M.; Nikolić, G. Alginates and similar exopolysaccharides in biomedical applications and pharmacy: Controlled delivery of drugs. *Adv. Technol.* **2016**, *5*, 39.
- [4] Camponeschi, F.; Atrei, A.; Rocchigiani, G.; Mencuccini, L.; Uva, M.; Barbucci, M. New formulations of polysaccharide-based hydrogels for drug release and tissue engineering. *Gels* **2015**, *1*, 3.
- [5] Pasqui, D.; De Cagna, M.; Barbucci, R. Polysaccharide-based hydrogels: The key role of water in affecting mechanical properties. *Polymers* **2012**, *4*, 1517.
- [6] Burey, P.; Bhandari, B. R.; Howes, T.; Gidley, M. J. Hydrocolloid gel particles: Formation, characterization, and application. *Crit. Rev. Food Sci. Nutr.* **2008**, *48*, 361.
- [7] Rodrigues, J. R.; Lagoa, R. Copper ions binding in Cu-alginate gelation. *J. Carbohydr. Chem.* **2006**, *25*, 219.
- [8] Yamamoto, K.; Yuguchi, Y.; Stokke, B.T.; Sikorski, P.; Bassett, D.C. Local structure of Ca²⁺ alginate hydrogels gelled via competitive ligand exchange and measured by small angle X-Ray scattering. *Gels* **2019**, *5*, 3.
- [9] Running, C. A., Falshaw, R.; Janaswamy, S. Trivalent iron induced gelation in lambda-carrageenan. *Carbohydr. Pol.* **2012**, *87*, 2735.
- [10] Funami, T.; Noda, S.; Nakauma, M.; Ishihara, S.; Takahashi, R.; Al-Assaf, S.; Ikeda, S.; Nishinari, K.; Phillips, G. O. Molecular structures of gellan gum imaged with atomic force microscopy in relation to the rheological behavior in aqueous systems in the presence or absence of various cations. *J. Agric. Food Chem.* **2008**, *56*, 8609.
- [11] Picone, C. S. F.; Cunha, R. L. Influence of pH on formation and properties of gellan gels. *Carbohydr. Pol.* **2011**, *84*, 662.
- [12] Fraeye, I.; Duvetter, T.; Doungla, E.; Van Loey, A.; Hendrickx, M. Fine-tuning the properties of pectin calcium gels by control of pectin fine structure, gel composition and environmental conditions. *Trends Food Sci. Technol.* **2010**, *21*, 219e228.

- 1
2
3 [13] Swamy, B. Y.; Yun, Y. S. *In vitro* release of metformin from iron(III) cross-linked alginate–
4 carboxymethyl cellulose hydrogel beads. *Int. J. Biol. Macromol.* **2015**, *77*, 114.
5
6 [14] Perez-Moral, N.; Gonzalez, M. C.; Parker, R. Preparation of iron-loaded alginate gel beads and
7 their release characteristics under simulated gastrointestinal conditions. *Food Hydrocoll.* **2013**,
8 *31*, 114.
9
10 [15] Banerjee, A.; Nayak, D.; Lahiri, S. A new method of synthesis of iron doped calcium alginate
11 beads and determination of iron content by radiometric method. *Biochem. Eng. J.* **2007**, *33*,
12 260.
13
14 [16] Rayment, P.; Wright, P.; Hoad, C.; Ciampi, E.; Haydock, D.; Gowland, P.; Butlera, M. F.
15 Investigation of alginate beads for gastro-intestinal functionality, part 1: *in vitro*
16 characterisation. *Food Hydrocoll.* **2009**, *23*, 816e822.
17
18 [17] Rosales, E.; Iglesias, O.; Pazos, M.; Sanromán, M. A. Decolourisation of dyes under electro-
19 Fenton process using Fe alginate gel beads. *J. Hazard. Mat.* **2012**, *213–214*, 369.
20
21 [18] Valenzuela, C.; Hernández, V.; Morales, M. S.; Neira-Carrillo, A.; Pizarro, F. Preparation and
22 characterization of heme iron-alginate beads. *LWT - Food Sci. Technol.* **2014**, *59*, 1283e1289.
23
24 [19] Alves, V. D.; Freitas, F.; Torres, C. A. V.; Cruz, M.; Marques, R.; Grandfils, C.; Gonçalves, M.
25 P.; Oliveira, R.; Reis, M. A. M. Rheological and morphological characterization of the culture
26 broth during exopolysaccharide production by *Enterobacter* sp. *Carbohydr. Pol.* **2010**, *81*, 758.
27
28 [20] Freitas, F.; Alves, V. D.; Gouveia, A. R.; Pinheiro, C.; Torres, C. A. V.; Grandfils, C.; Reis, M.
29 A. M. Controlled production of exopolysaccharides from *Enterobacter* A47 as a function of
30 carbon source with demonstration of their film and emulsifying abilities. *Appl. Biochem.*
31 *Biotechnol.* **2014**, *172*, 641.
32
33 [21] Freitas, F.; Alves, V. D.; Torres, C. A. V.; Cruz, M.; Sousa, I.; Melo, M. J.; Ramos, A. M.; Reis,
34 M. A. M. Fucose-containing exopolysaccharide produced by the newly isolated *Enterobacter*
35 strain A47 DSM 23139. *Carbohydr. Polym.* **2011**, *83*, 159.
36
37 [22] Torres, C. A. V.; Ferreira, A. R. V.; Freitas, F.; Reis, M. A. M.; Coelho, I.; Sousa, I.; Alves, V.
38 D. Rheological studies of the fucose-rich exopolysaccharide FucoPol. *Int. J. Biol. Macromol.*
39 **2015**, *79*, 611.
40
41 [23] Lourenço, S. C.; Torres, C. A. V.; Nunes, D.; Duarte, P.; Freitas, F.; Reis, M. A. M.; Fortunato,
42 E.; Martins, M. M.; da Costa, L. B.; Alves, V. D. Using a bacterial fucose-rich polysaccharide
43 as encapsulation material of bioactive compounds. *Int. J. Biol. Macromol.* **2017**, *104*, 1099.
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3 [24] Dhadge, V. L.; Morgado, P. I.; Freitas, F.; Reis, M. A. M.; Azevedo, A.; Aires-Barros, R.;
4 Roque, A. C. A. An extracellular polymer at the interface of magnetic bioseparations. *J. Royal*
5 *Soc. Interface* **2014**, *11*, 20140743.
6
7 [25] Palma, S. I. C. J.; Rodrigues, C. A. V.; Carvalho, A.; Morales, M. del P.; Freitas, F.; Fernandes,
8 A. R.; Morales M. P.; Cabral, J. M. S.; Roque, A. C. A. A value-added exopolysaccharide as a
9 coating agent for MRI nanoprobos. *Nanoscale* **2015**, *7*, 14272.
10
11 [26] Shimada, A.; Nakata, H.; Nakamura, I. Acidic exopolysaccharide produced by *Enterobacter* sp.
12 *J. Ferment. Bioeng.* **1997**, *84*, 113.
13
14 [27] Sutradhar, M.; Fernandes, A. R.; Silva, J.; Mahmudov, K. T.; Guedes da Silva, M. F. C.;
15 Pombeiro, A. J. L. Water soluble heterometallic potassium-dioxidovanadium(V) complexes as
16 potential antiproliferative agents. *J. Inorg. Biochem.* **2016**, *155*, 17.
17
18 [28] Vinhas, R.; Fernandes, A. R.; Baptista, P. V. Gold nanoparticles for BCR-ABL1 gene silencing:
19 Improving tyrosine kinase inhibitor efficacy in chronic myeloid leukemia. *Mol. Ther. - Nucleic*
20 *Acids* **2017**, *7*, 408.
21
22 [29] Fernandes, A. R.; Jesus, J.; Martins, P.; Figueiredo, S.; Rosa, D.; Martins, L. M. R. D. R. S.;
23 Corvo, M. L.; Carvalheiro, M. C.; Costa, P. M.; Baptista, P. V. Multifunctional gold-
24 nanoparticles: a nanovectorization tool for the targeted delivery of novel chemotherapeutic
25 agents. *J. Control Release* **2017**, *245*, 52.
26
27 [30] Strobber, W. Trypan blue exclusion test of cell viability. In *Current Protocols in Immunology*;
28 John Wiley & Sons, Inc.: Hoboken, NJ, USA; Vol. Appendix 3, p Appendix 3B, 2001.
29
30 [31] Araújo, D.; Concórdio-Reis, P.; Marques, A. C.; Sevrin, C.; Grandfils, C.; Alves, V. D.;
31 Fortunato, E.; Reis, M. A. M.; Freitas, F. Demonstration of the ability of the bacterial
32 polysaccharide FucoPol to flocculate kaolin suspensions. *Environ. Technol.* **2019**, 1–9.
33 <https://doi.org/10.1080/09593330.2018.1497710>
34
35 [32] Farinha, I.; Duarte, P.; Pimentel, A.; Plotnikova, E.; Chagas, B.; Mafra, L.; Grandfils, C.; Freitas,
36 F.; Fortunato, E.; Reis, M. A. M. Chitin-glucan complex production by *Komagataella pastoris*:
37 downstream optimization and product characterization. *Carbohydr Pol* **2015**, *130*, 455-464.
38
39 [33] Synytsya, A.; Copikova, J.; Matejka, P.; Machovic, V. Fourier transform Raman and infrared
40 spectroscopy of pectins. *Carbohydr. Pol.* **2003**, *54*, 97-106.
41
42 [34] Pramanik, A.; Maiti, S.; Mahanty, S. Metal hydroxides as a conversion electrode for lithium-ion
43 batteries: a case study with a Cu(OH)₂ nanoflower array. *J. Mater. Chem. A* **2014**, *2*, 18515.
44
45 [35] Abd El-Mohdy, H. L. Radiation synthesis of nanosilver/poly vinyl alcohol/cellulose
46 acetate/gelatin hydrogels for wound dressing. *J. Pol. Res.* **2013**, *20*, 177.
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3 [36] Ruiz, L. M.; Jenssen, E. L.; Rossel, Y.; Puaș, G. I.; Gonzalez-Ibanez A. M.; Bustos, R. I.;
4 Ferrick, D. A.; Elorza, A. A. Non-cytotoxic copper overload boosts mitochondrial energy
5 metabolism to modulate cell proliferation and differentiation in the human erythroleukemic cell
6 line K562. *Mitochondrion* **2016**, *29*, 18.
7
8
9 [37] Vinhas, R.; Lourenço, L.; Santos, S.; Ribeiro, P.; Silva, M.; de Sousa, A. B.; Baptista, P. V.;
10 Fernandes, A. R. A double Philadelphia chromosome-positive chronic myeloid leukemia
11 patient, co-expressing P210BCR-ABL1 and P195BCR-ABL1 isoforms. *Haematologica* **2018**,
12 *103(11)*: e549–e552.
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table 1. Results obtained with the different tested methods (no alteration, (-); formation of a precipitate, pp; weak gel formation, (+); strong gel formation, ()); not tested, x).

Salt	Deionized water	NaOH 2 M
NaCl	(-)	(-)
KCl	(-)	(-)
CaCl ₂	(-)	pp
MgSO ₄	(-)	(-)
CuSO ₄	(-)	(++)
ZnSO ₄	(-)	(-)
FeCl ₃	(++)	x

Table 2. Main characteristics of the metal-FucoPol beads (Fe-P, iron-FucoPol; Cu-P, copper-FucoPol; Fe/Cu-P, iron- and copper-FucoPol).

Parameter	Fe-P	Cu-P	Fe/Cu-P
Shape	Spherical	Spherical	Spherical
Color	Yellow	Blue	Dark orange
Diameter (mm)	2.0 – 3.0	3.0 – 4.0	1.5 – 2.0
Mass (mg)	7.90±0.002	50.59±0.006	9.28±0.002
Water content (wt%)	98.60±0.26	99.84±0.06	99.27±0.47
Metal content (µg/bead)			
Copper	---	134.50±29.63	118.33±20.54
Iron	11.54±1.09	---	11.84±3.21

Table 3. Iron and/or copper release from the Fe-P, Cu-P and Fe/Cu-P beads (Fe-P, iron-FucoPol; Cu-P, copper-FucoPol; Fe/Cu-P, iron- and copper-FucoPol) in different media, after 24 h (all tests were performed at 25 °C, except in DMEM, for which experiments were conducted also at 37 °C).

Media	Fe-P beads	Cu-P beads	Fe/Cu-P beads	
	[Fe] (mg L ⁻¹)	[Cu] (mg L ⁻¹)	[Fe] (mg L ⁻¹)	[Cu] (mg L ⁻¹)
Water	0.00±0.00	0.25±0.06	0.01±0.00	0.15±0.03
NaCl 0.9%	0.01±0.00	0.08±0.02	0.00±0.00	0.12±0.02
PBS	0.18±0.02	0.08±0.02	0.01±0.00	0.12±0.02
SGF	*	*	*	*
SIF	0.19±0.02	*	0.00±0.00	0.03±0.00
DMEM-FBS				
25 °C	0.00±0.00	*	0.00±0.00	0.02±0.00
37 °C	0.00±0.00	*	0.00±0.00	0.98±0.17

* beads disintegration

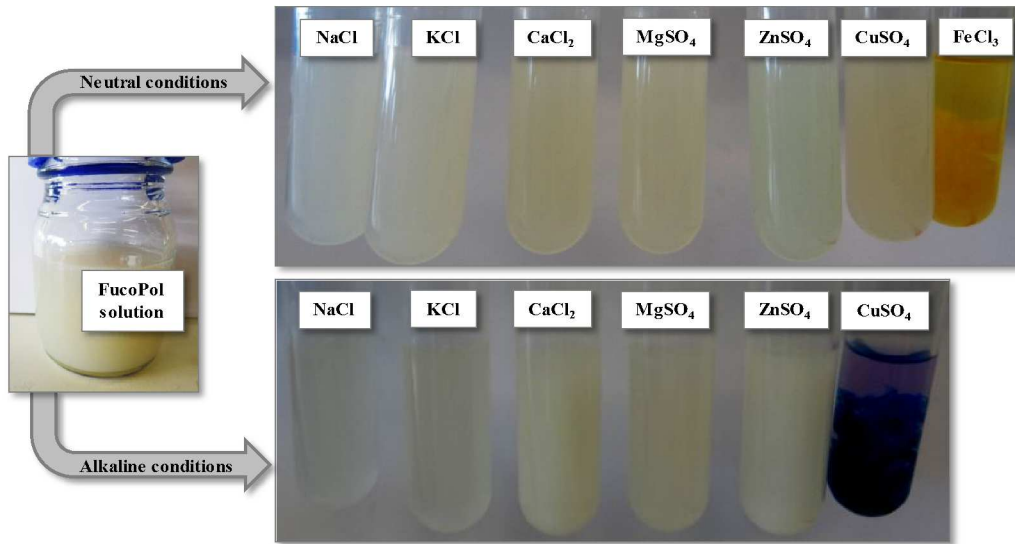


Figure 1

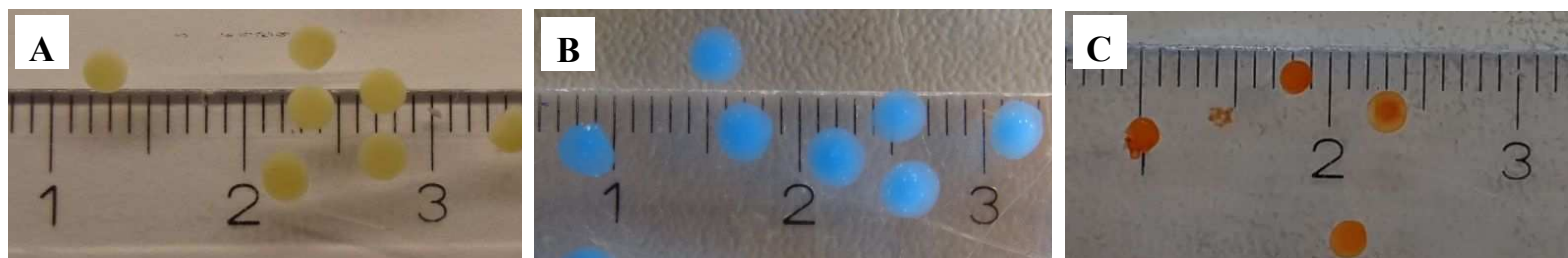


Figure 2

For Peer Review Only

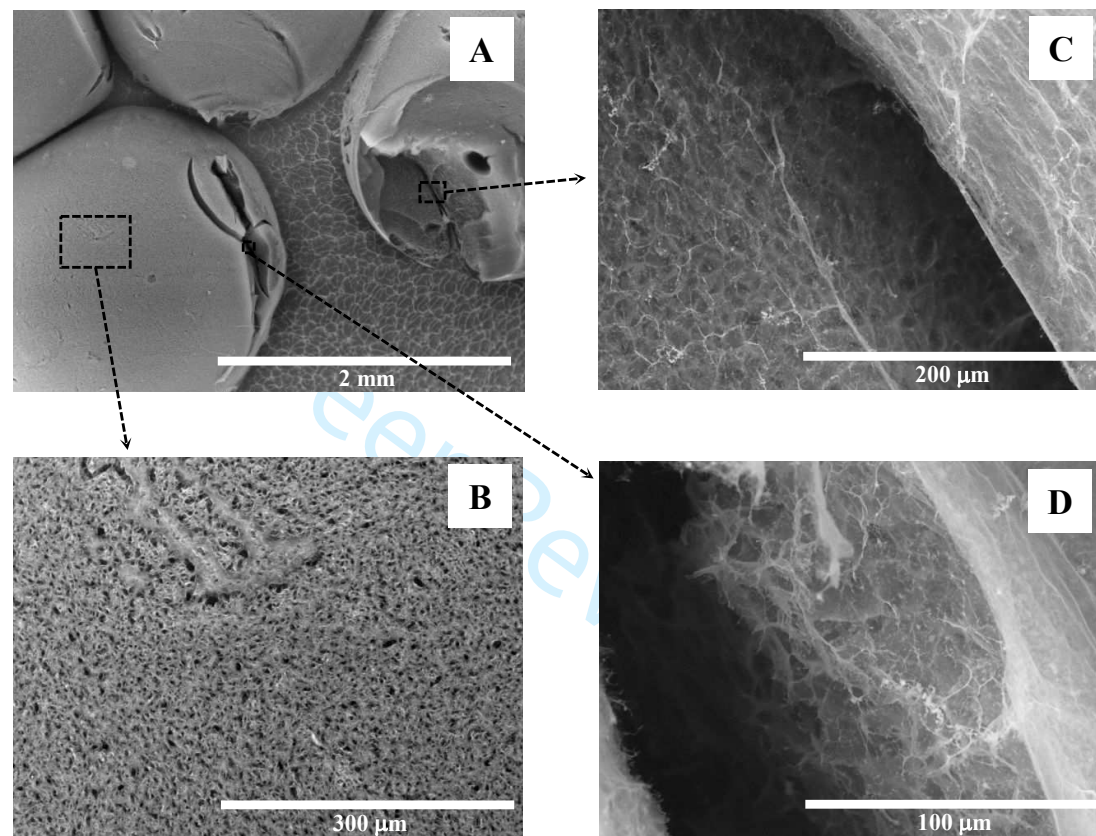


Figure 3

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47

6
7
8

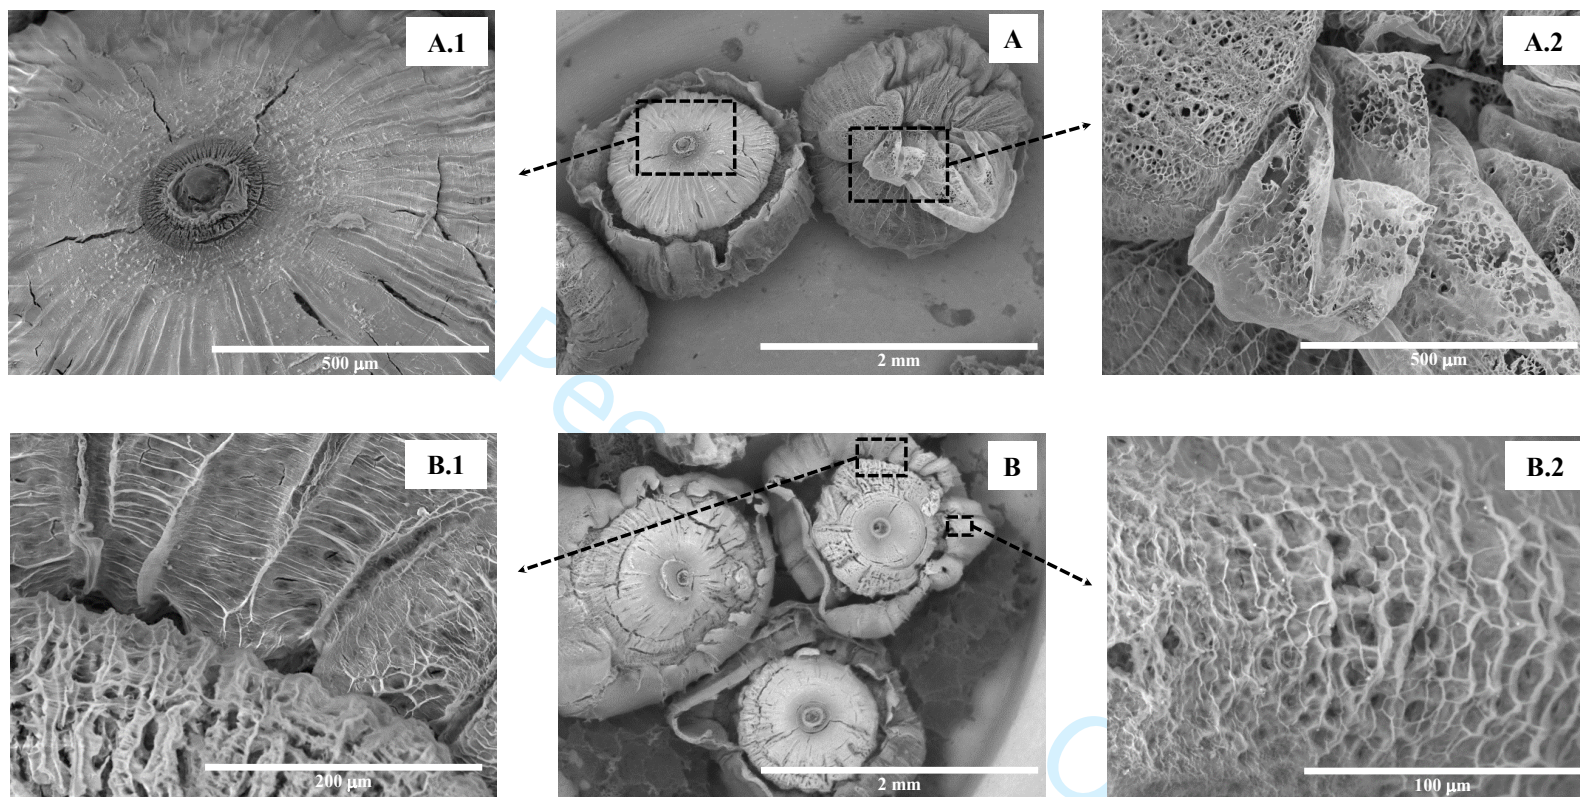


Figure 4

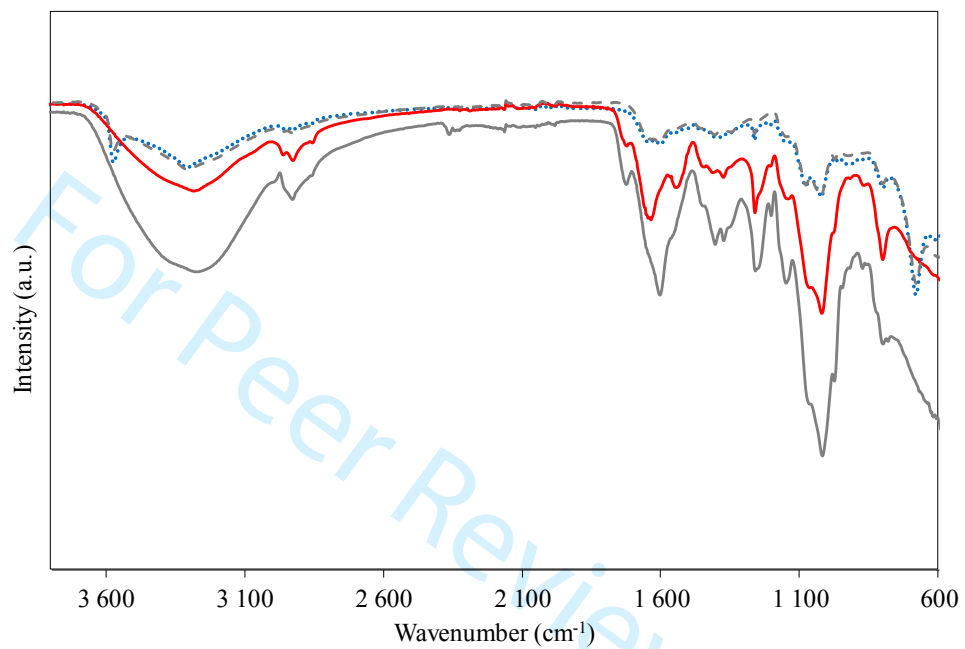


Figure 5

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47

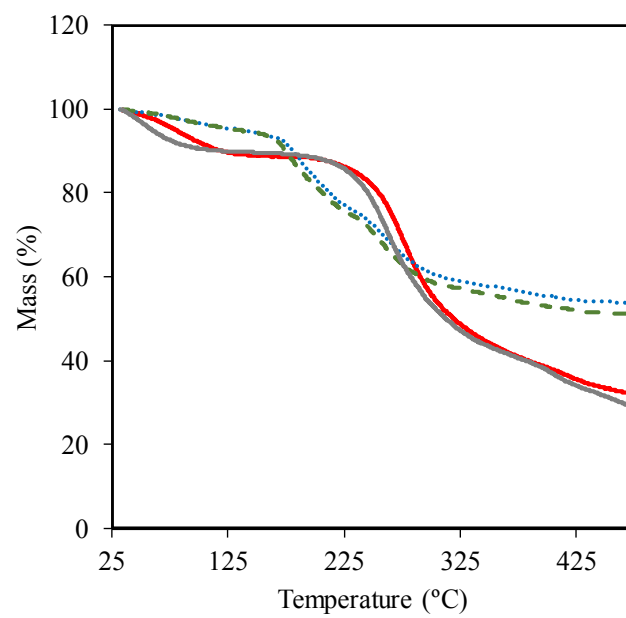


Figure 6

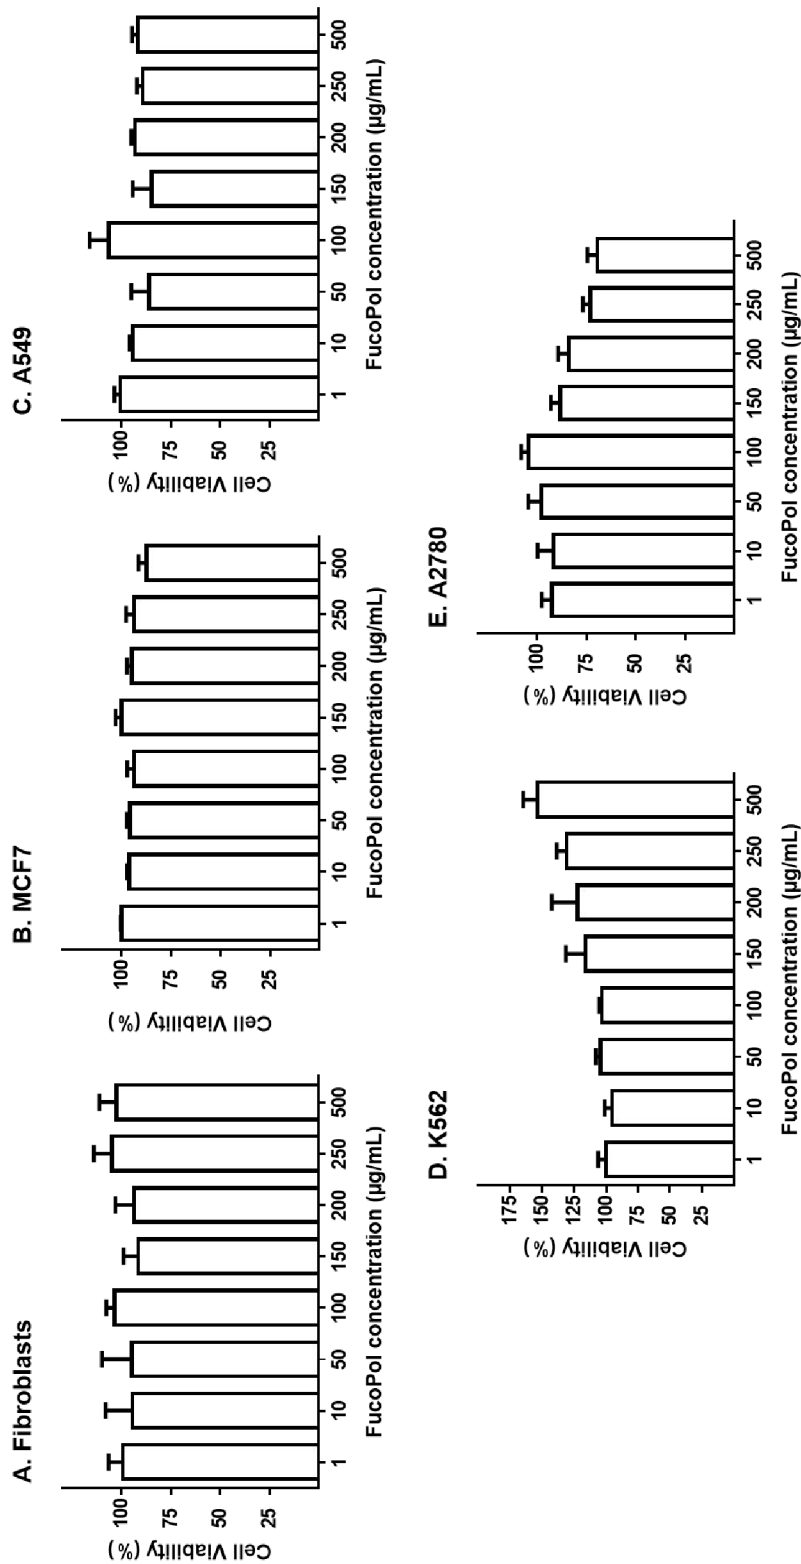


Figure 7

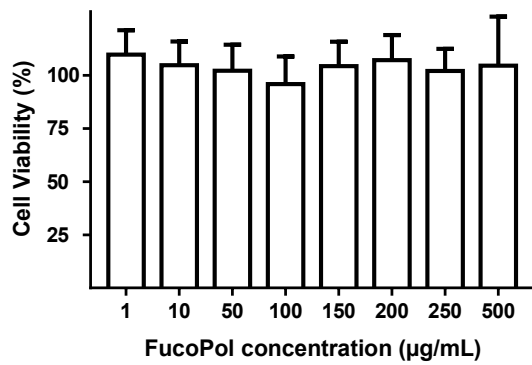


Figure 8

21

22

23

For Peer Review Only

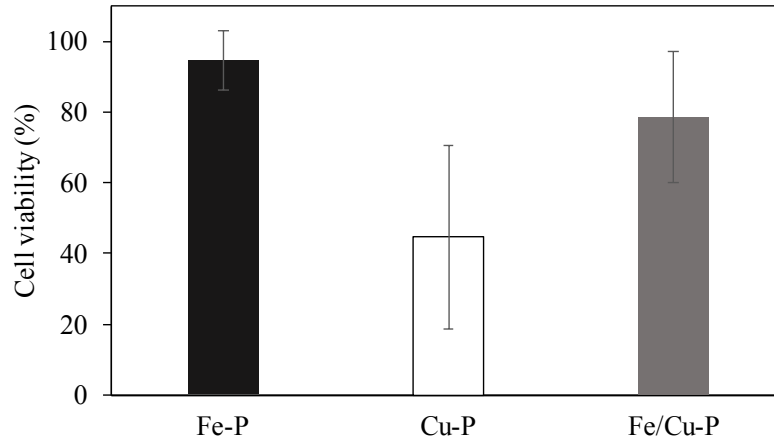


Figure 9

24
25
26

Or Peer Review Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 **27 Figure captions**
4

5
6 28 Figure 1. Original FucoPol solution and the results of the tests made to assess gel formation
7 29 with different salts, under neutral conditions (upper image) or alkaline conditions (lower
8 30 image).
9

10
11 31 Figure 2. FucoPol hydrogel beads: (A) Fe-P beads; (B) Cu-P beads; (C) Fe/Cu-P beads.
12

13
14 32 Figure 3. SEM images of hydrated Fe-P beads at a temperature of -4 °C.
15

16
17 33 Figure 4. SEM images of hydrated Fe/Cu-P beads at a temperature of -4 °C.
18

19 34 Figure 5. FTIR spectra of FucoPol (full grey line) and dried FucoPol gel beads: Fe-P (full red
20 35 line), Cu-P (dotted line), Fe/Cu-P (dashed line).
21
22

23 36 Figure 6. Thermogravimetric analysis of FucoPol (full grey line) and dried FucoPol gel
24 37 beads: Fe-P (full red line), Cu-P (dotted line), Fe/Cu-P (dashed line)
25
26

27 38 Figure 7. Cytotoxicity of FucoPol in normal human dermal fibroblasts (A), breast
28 39 adenocarcinoma cell line MCF-7 (B), lung adenocarcinoma cell line A549 (C), Chronic
30 40 myelogeneous leukemia cell line K562 (D) and ovarian carcinoma cell line A2780 (E). Cells
31 41 were treated with increasing concentrations of polymer for 48 h and cell viability was
32 42 determined by the MTS assay. Data was normalized against the control (cells grown without
33 43 polymer) and expressed as average \pm standard error mean of three independent assays.
34
35
36
37

38 44 Figure 8. Viability accessed using Trypan Blue exclusion method of K562 cells treated with
39 45 FucoPol. Cells were treated with increasing concentrations of polymer for 48 h and cell
40 46 viability was determined. Data was normalized against the control (cells grown without
41 47 polymer) and expressed as average \pm standard error mean of three independent assays.
42
43
44

45 48 Figure 9. Viability of K562 cells in the presence of 150 mg Fe-P (black bars), Cu-P (white
46 49 bar) and Fe/Cu-P (grey bar) beads after 48 hours incubation. Viability was accessed using the
47 50 Trypan Blue exclusion method, normalized to the control (cells grown in non-supplemented
48 51 medium) and represented as the average \pm SEM of three independent assays.
49
50
51
52

53
54
55
56
57
58
59
60